



LABORATORI NAZIONALI DI FRASCATI

SIS – Pubblicazioni

LNF-96/044 (R)
10 Settembre 1996

AC Susceptibility Measurements of YBCO Sintered Pellets Loaded with Hydrogen by μs Pulsed Electrolysis

D. Di Gioacchino, M. Boutet, A. Spallone, P. Tripodi, F. Celani

INFN–Laboratori Nazionali di Frascati, P.O. Box 13, I-00044 Frascati (Rome), Italy

ABSTRACT

The research about the hydrogen in metals has attracted the attention for reasons motivated both from a basic as well as an applied point of view. It is evident there is an overlap between these approaches. Some possible application are discussed in [18].

Actually there is a general interest in the dynamics of hydrogen (or deuterium) in metals, since these are linked with many physical properties of such systems, in particular superconductivity, electronic properties, and hydrogen diffusion, a great abundance of experimental research exists in this field. Our aim is to study the effects of hydrogen (and deuterium) on superconducting features of metals (as Pd, Ni and so on) and of high critical temperature superconducting compounds $\text{Y}_1\text{Ba}_2\text{Cu}_3\text{O}_7$ (YBCO).

In this chapter we will deal with the hydrogen loading of YBCO. The hydrogen charging has been performed by means an innovative electrochemical procedure, using

very high peak current (up to 15.2 A) with a short time duration (1.3-5 μs) with a repetition rate of 5 kHz. The procedure has been performed at room temperature in an aqueous environment.

1. BACKGROUND.

The variations of the onset of the superconducting transition temperatures (T_{on}) of YBCO loaded with hydrogen using high pressure gas have been studied by some authors [1-4], giving different relations between the transition temperature and the hydrogen content. It has been shown that hydrogen can decrease [16] or increase [1, 2] the critical temperature depending on its stoichiometry and on the kind of bonds with Cu. The hydrogen atoms preferably occupy oxygen vacancies in sites on Cu(1)O plane and Cu(2)O₂ plane [2] or only Cu(2)O₂ plane [16]. However, a general worsening of the superconducting grain coupling is observed [3]. The effects of deuterium have not been

deeply analyzed yet.

In the past we studied the gas loading of YBCO with hydrogen and deuterium. In a paper [5] we described the enhancement of the onset transition temperature of sintered YBCO by means of a loading procedure using deuterium gas with a pressure between 38 and 53 bar and a complex thermal cycle. After the deuterium gas loading non-superconducting phases were not detected by X-ray diffraction. A deuterated YBCO pellet exhibited a superconducting transition temperature up to 100 K (-173 °C) and the absence of a significant weakening of the superconducting grain coupling; another sample showed a T_{on} up to 102 K under 35 bar of deuterium gas pressure; we obtained a maximum T_{on} of 97.5 K loading with hydrogen. The D/YBCO ratio was up to 1, measured by drop pressure and by weighting. After the deuterium loading non-superconducting phases were not detected by X-ray diffraction.

Our experience is that these processes often lead to the deterioration and, in the worst cases, to the destruction of the sample; moreover the gas loading usually decreases the intergranular coupling. Anyway the deterioration is strongly dependent on the pellet quality.

Since the hydrogen diffusion strongly depends on its penetration on the pellet surface, which increases with the pressure, our purpose is to study the hydrogen loading at room temperature at very high pressures (> 1000

atm). High pressure means, first of all, strong intermolecular interactions, due to the increasing density of the particles. The high density is often followed by a rearrangement of the lattice, with a variation of the lattice parameter. It seems quite probably that a metallic behaviour of the hydrogen involved can be achieved due to the high pressure. It is very hard to reach very high pressures by the gas loading procedures and it requires different thermal cycles [3] in order to activate the charging process. For these reasons it is necessary a more efficient and safe charging experimental set-up, which should avoid the drawbacks of the gas loading.

In this chapter we will describe the only procedure that we know for this purpose: the electrolysis. The room temperature electrochemical loading of cathodically polarized metal with hydrogen is a procedure widely used [6]. In addition to the simplicity of the experimental set-up, the electrolysis allows to obtain extremely high hydrogen and/or deuterium equivalent pressure on the surface of the cathode. In fact, by a Nerst-type expression [7, 8]: the hydrogen equivalent pressure increases exponentially with the effective cathodic overpotential η_2' , which is the potential difference between the cathode and the platinized-platinum reference electrode, measured after that the electrolysis has been switched off (typically after 30 μ s) [7, 8], so that it is only a fraction of the whole overpotential. If we impose, for example, a

cathodic voltage of -100 mv, relative to a hydrogen electrode in the same solution, the equivalent pressure in the "dynamic" regime is on the order of 2400 atm, but substituting in the Nerst-type equation the effective value η_2' the effective equivalent pressure is much lower (on the order of 9 atm) [8]. For instance, even the gold has got a dynamic overpotential different from zero, but as soon as the electrolysis is switched off, it quickly reaches zero (in fact it is well known that the gold can not be loaded with hydrogen). For these reasons, in order to be sure to reach large effective pressures, as high as possible overpotentials are necessary.

As regards the dc electrolysis large values of currents are not available, not only due to the intrinsic current saturation limit, but mainly because the evolution of the hydrogen bubbles on the cathode forbids the electrochemical process. For these reasons in this chapter, in order to reach larger overpotential values and much higher equivalent pressure, the μ s pulsed electrochemical technique has been explored. This method has been set by our staff for the charging of different metals, as palladium, to very high D/Pd ratio (up to 1.2) at room temperature [9]. In the pulsed electrolysis the hydrogen bubbles are not a serious problems and the existence of intrinsic current limits in dynamical conditions is not yet clear. Using high current (overpotential) peaks, higher loadings should be available since the electrochemical cell works always far away

from the saturation conditions.

The YBCO pellet is the cathode of an aqueous solution containing the electrolyte, LiOH 0.3 M, and is polarized by short (1.3–5 μ s) and high power peaks with a low duty-cycle at room temperature.

In section II the samples preparation and the experimental apparatus used to characterize and to load the samples are described. The pellets have been characterized by the X-ray diffraction and, measured as a function of the temperature, by the ac magnetic susceptibility. In section III the loading procedures and the results are reported and discussed. In some conditions the YBCO pellets exhibited an enhancement of the transition temperature up to 95.4 K without a significant weakening of the superconducting grain coupling. These effects appear strongly dependent on the loading conditions.

2. SAMPLES PREPARATION AND EXPERIMENTAL APPARATA.

The YBCO pellets have been prepared following a modified citrate pyrolysis procedure and only two subsequent thermal treatments (calcination and sinterization) in ozone-enriched atmosphere [11]. The typical sample dimensions (within 5%) have a diameter and a height respectively equal to 20 mm. and 5 mm. These samples do not show spurious phases in the limit of the X-ray diffraction sensitivity. Moreover their chemical stability in aqueous environments is enough for

our purposes: the superconducting features are not significantly affected by a 20 hours immersion in distilled water.

In order to have the possibility of testing the superconducting features of the loaded samples, they have been characterized by measurements of ac shielding properties.

The ac magnetic susceptibility has been measured using a two-coils coaxial susceptometer. The external coil generates the ac magnetic field, the inner one is the pick-up coil. The reported measurements have been obtained after subtraction of instrumental blank, stored in the data-acquisition computer. The blank measurements have been performed by substituting the superconducting sample with a teflon disk of the same geometrical dimensions. In spite of the higher sensitivity of a bridge configuration, the simpler two-coils system avoids the frequency dependent balance; moreover, the large volume of the pellets do not require, in our measurements, high signal sensitivity. In order to detect χ' and χ'' , we acquire the in-phase and the out-of-phase voltage signals at the pick-up coil by a lock-in amplifier (EG&G 5208). The susceptometer calibration, and in particular the real part χ' of the susceptibility, has been previously obtained (at 4.2 K) by means of lead samples with the same shape of the pellets. In our measurements the amplitude of the ac magnetic field H_0 is equal to 0.2 or 1 G at the frequency of 107 or 1070 Hz. The local earth magnetic field was shielded at 0.2 G. The

temperature is measured by a silicon diode (DT470SD12, Lake Shore Cryotronics), in good thermal contact with the sample, through an high-resolution temperature controller (DR91C, Lake Shore Cryotronics). Starting from room temperature, the samples are cooled down to $T=77$ K with a decreasing rate of 15 K/min under the ac applied magnetic field (Field Cooling, FC). After at least one hour at 77 K the measurements have been performed with a warming up rate of 0.3 K/min, up to room temperature.

The measured quantities are recorded by a computer-controlled acquisition system by HP-IB bus. In fig. 1a the experimental apparatus used to perform the μ s pulsed electrolysis is reported. The pulses, with negative polarity, are obtained by means of an home-made capacitive-discharge pulse generator.

The power pulse generator (PPG) supplies high peak power (up to 1.2 kW) with a high repetition rate (up to 10 kHz) and high peak current density on the YBCO surface (3 A/cm^2). Between the output of the PPG and the input of the electrolytic cell there is a fast-power diode D1 (40HFL80S05). In this way we can avoid the self-discharging phenomena of the electrolytical cell during the off-period of the pulser (typically 99%) and we obtain, at the same time, a self-polarization of the YBCO sample. In fig. 1b we describe a simplified scheme of the PPG.

We have chosen 3 main parameters to characterize the samples: the onset temperature

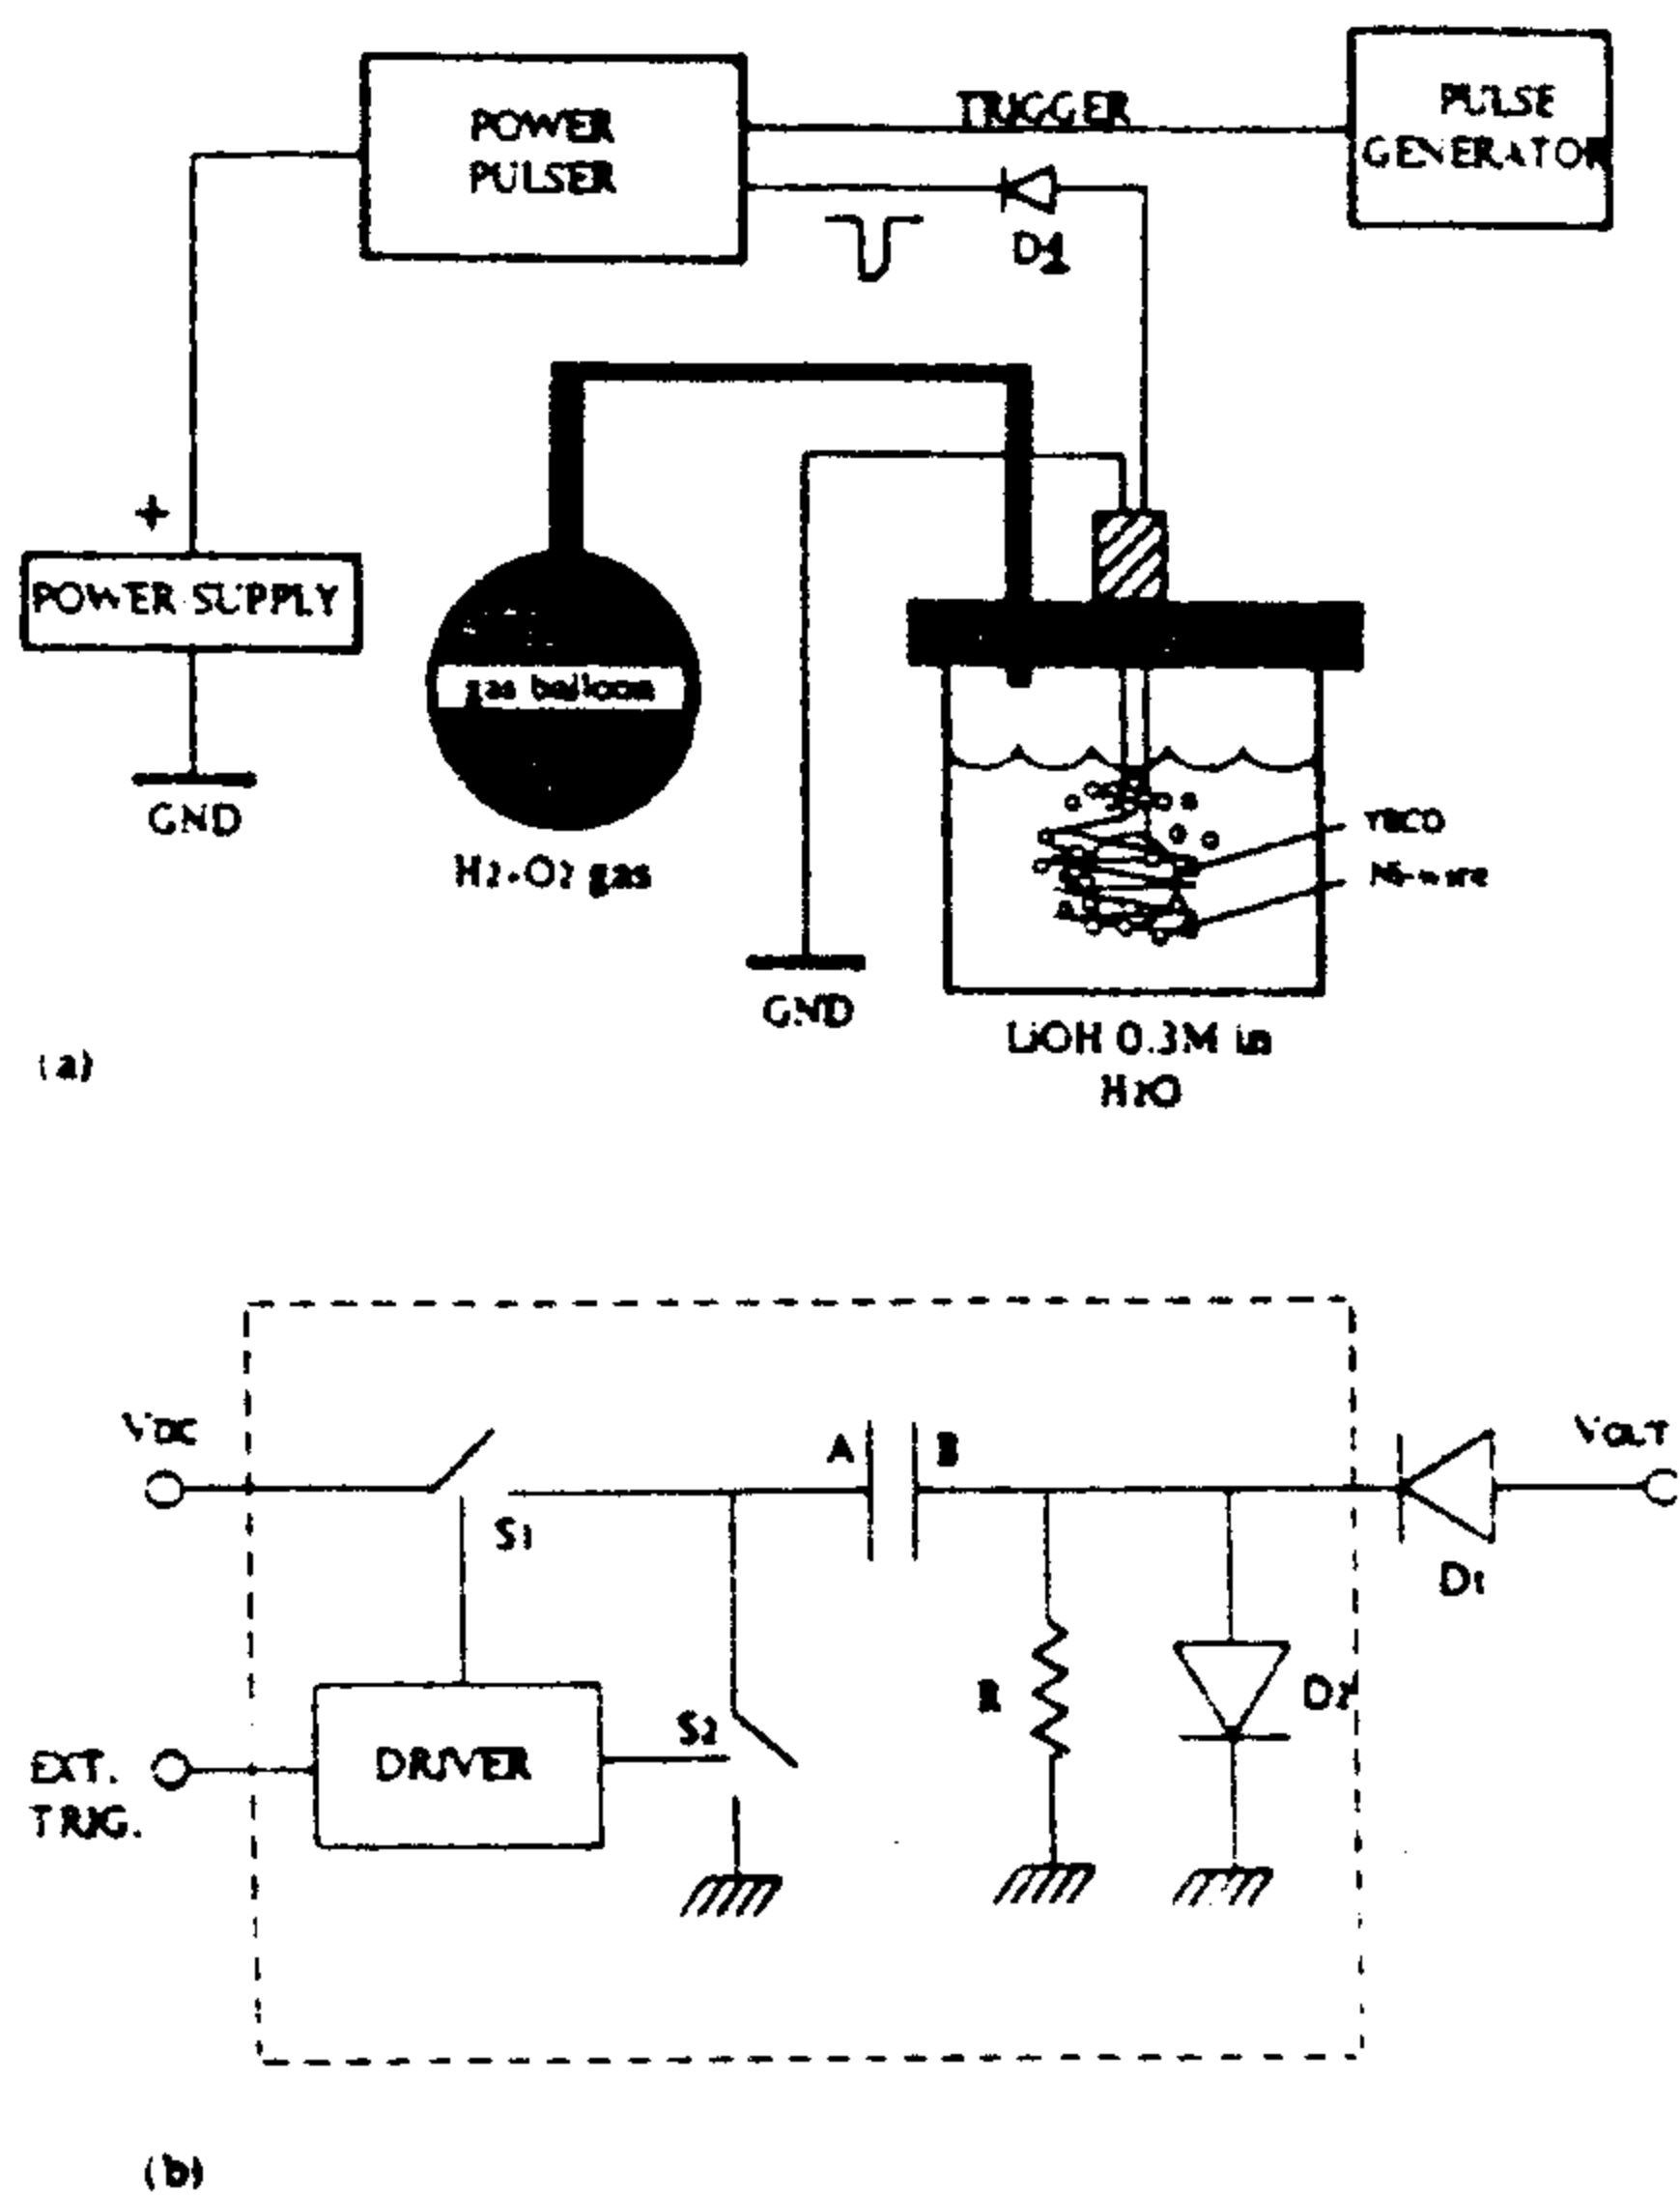


Fig. 1.(a) Experimental set-up for hydrogen loading by means μ s pulsed electrolysis. (b) Simplified scheme of the pulse power generator (PPG). The PPG is made by a driver, controlled by an external trigger, which drives the 2 switches, S₁ and S₂, in counter-phase. The switches allows the discharging of the capacitor through the electrolytical cell for a duration, supplying to the cell a pseudo-trapezoidal voltage signal. The pulses are fast (rise time < 200 ns, fall time < 300 ns) with an high repetition rate (up to 10 KHz). The high frequency is allowed by the 2 switches, which are active circuits, and by the fast recovery diode D₂ (1N4937A), which allows a fast restoring of the charge.

of the superconducting transition T_{ON} , the temperature T_p corresponding to the maximum of χ'' as a function of temperature and the FWHM (Full Width Half Maximum) of the peak of $\chi''(T)$.

The T_{ON} is defined as the temperature corresponding to the beginning of the deviation of χ' and χ'' from the normal state behaviour and its variation is related to the change of the superconducting properties of YBCO generated by the presence of hydrogen inside the grains.

The temperature T_p , following the Bean model and neglecting the demagnetization factor, corresponds to the full penetration conditions of the magnetic field: $J_c(T_p) = H_0/r$, where r is the radius of the pellet. In this way, for a given transition temperature, an increasing or a decreasing of T_p respectively correspond to an increasing or a decreasing of $J_c(T)$, at each temperature. In a granular system $J_c(T)$ is determined by the Josephson coupling between grains, so that a decreasing of $J_c(T)$ is the direct evidence of the increasing of non-superconducting phases in the grain boundaries and vice versa.

The value of the FWHM is a measurement of the intergranular coupling even if T_{ON} changes: greater is the superconducting coupling among the grains, lower is the FWHM value [10].

The thermal equilibrium of both measurement systems has been checked by means of measurements of the onset of the superconducting transition temperature of unloaded YBCO samples: they showed a T_{ON} of 91-92 K depending on the sample quality.

3. LOADING PROCEDURE AND RESULTS.

As previously described the gas loading

usually brings to a deterioration of the sample, moreover it is not safe to charge with hydrogen or deuterium gas under high pressure. Because of these reasons and others already explained in the introduction, we have tried to load the samples by an electrochemical method.

We prepared an aqueous solution of LiOH (0.3 M). The YBCO pellet is the cathode, around which we have wrapped a nickel-passivated wire, which is in good electrical contact with the sample and leads the current to it. The cathode is faced to the anode, made by a grounded nickel-passivated network.

In the pulsed electrolysis method the absorption rate into the bulk of the sample is to be optimized as a function of the width and height of the pulses. For this purpose we loaded several samples at room temperature, changing some parameters, but keeping constant the repetition rate of the pulses (5 kHz).

The first pellet (α) was charged imposing the pulse height equal to 12 V (5.5 A of peak current) and the width equal to 5 μ s; the loading lasted 20 hours.

In fig. 2 and 3 are respectively shown the real and imaginary part of magnetic susceptibility measured at 1 G and 107 Hz, before ($\alpha 1$) and after ($\alpha 2$) the charging. In fig. 2 we did not see any significant variation of the T_{0n} , but only a larger transition width with a lower value of the modulus of χ' at 77 K of $\alpha 2$ in respect to $\alpha 1$. In fig. 3 we observed a FWHM enlargement equal to 1.4 K in respect to the same

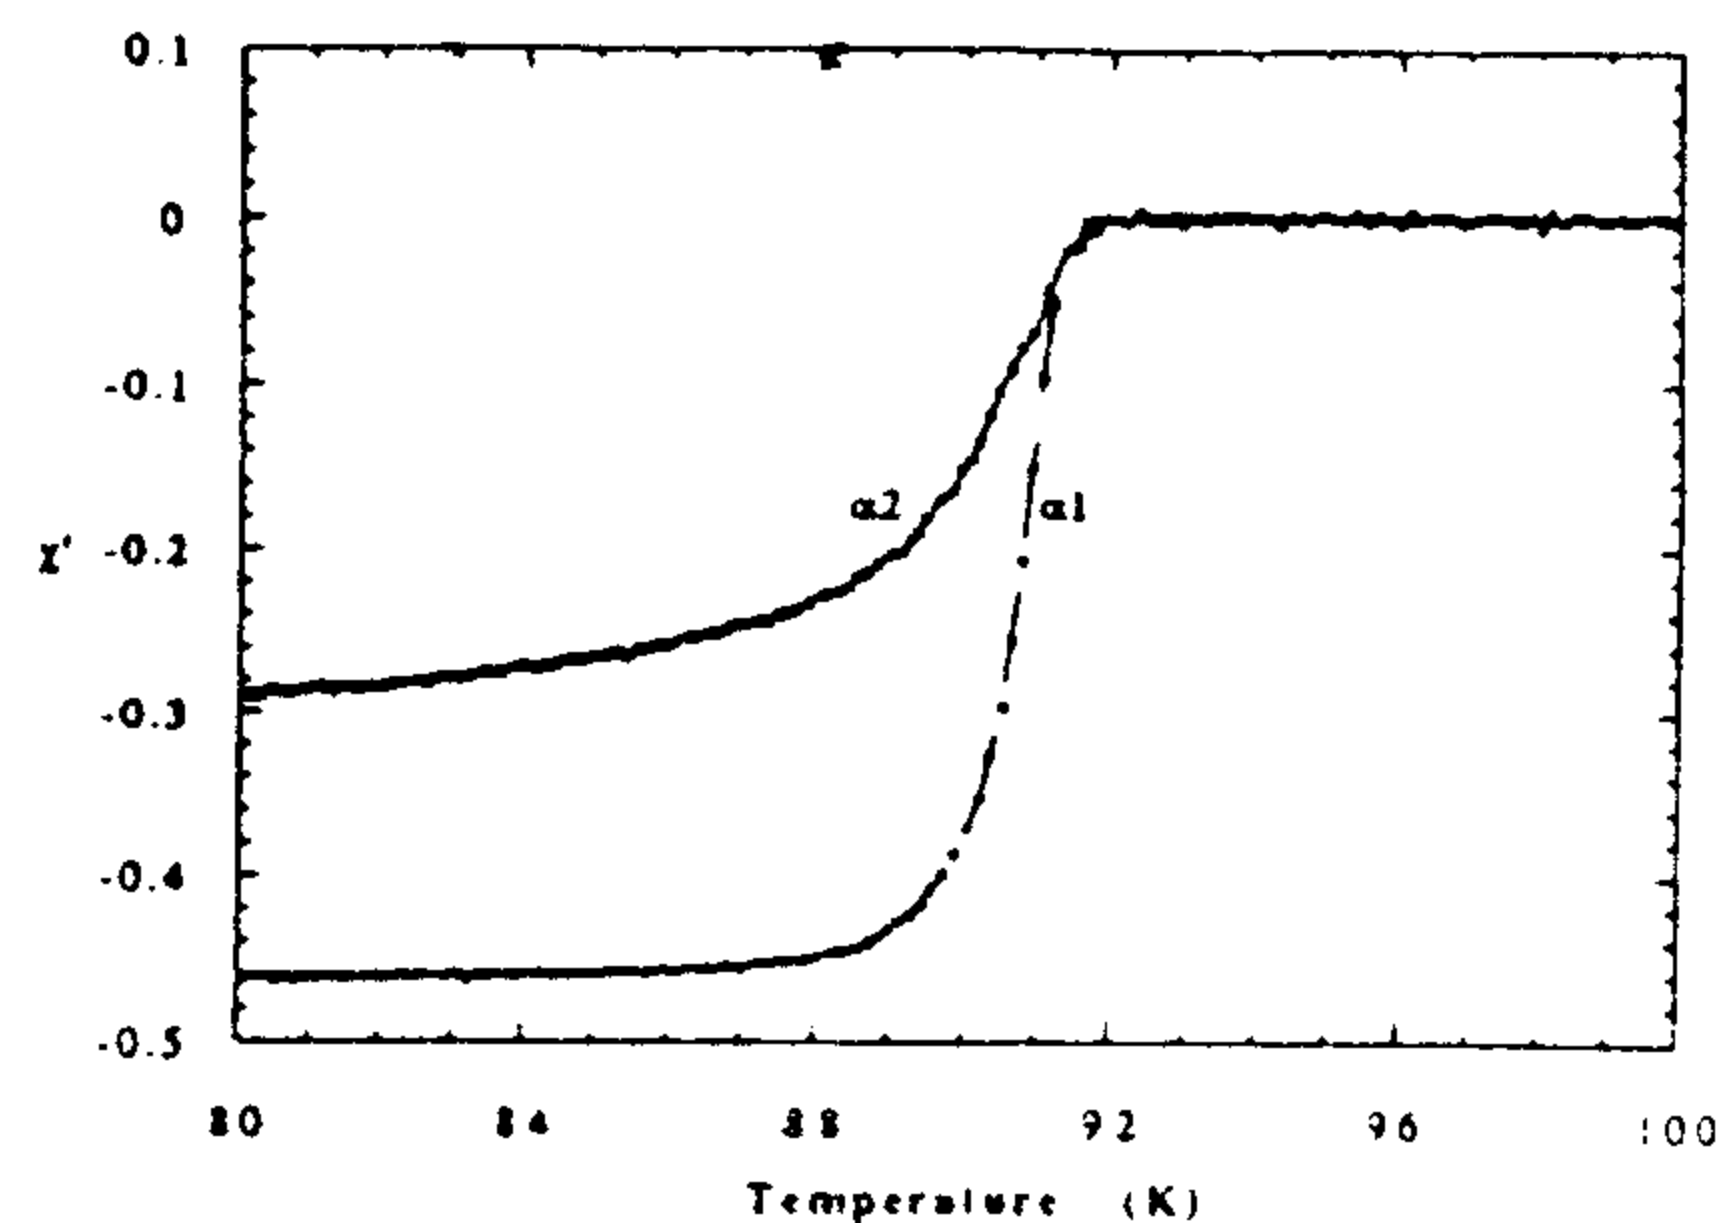


Fig. 2 - Real part of the magnetic susceptibility (χ') for the α sample. $\alpha 1$ YBCO pellet before H_2 loading; $\alpha 2$ YBCO sample after H_2 loading.

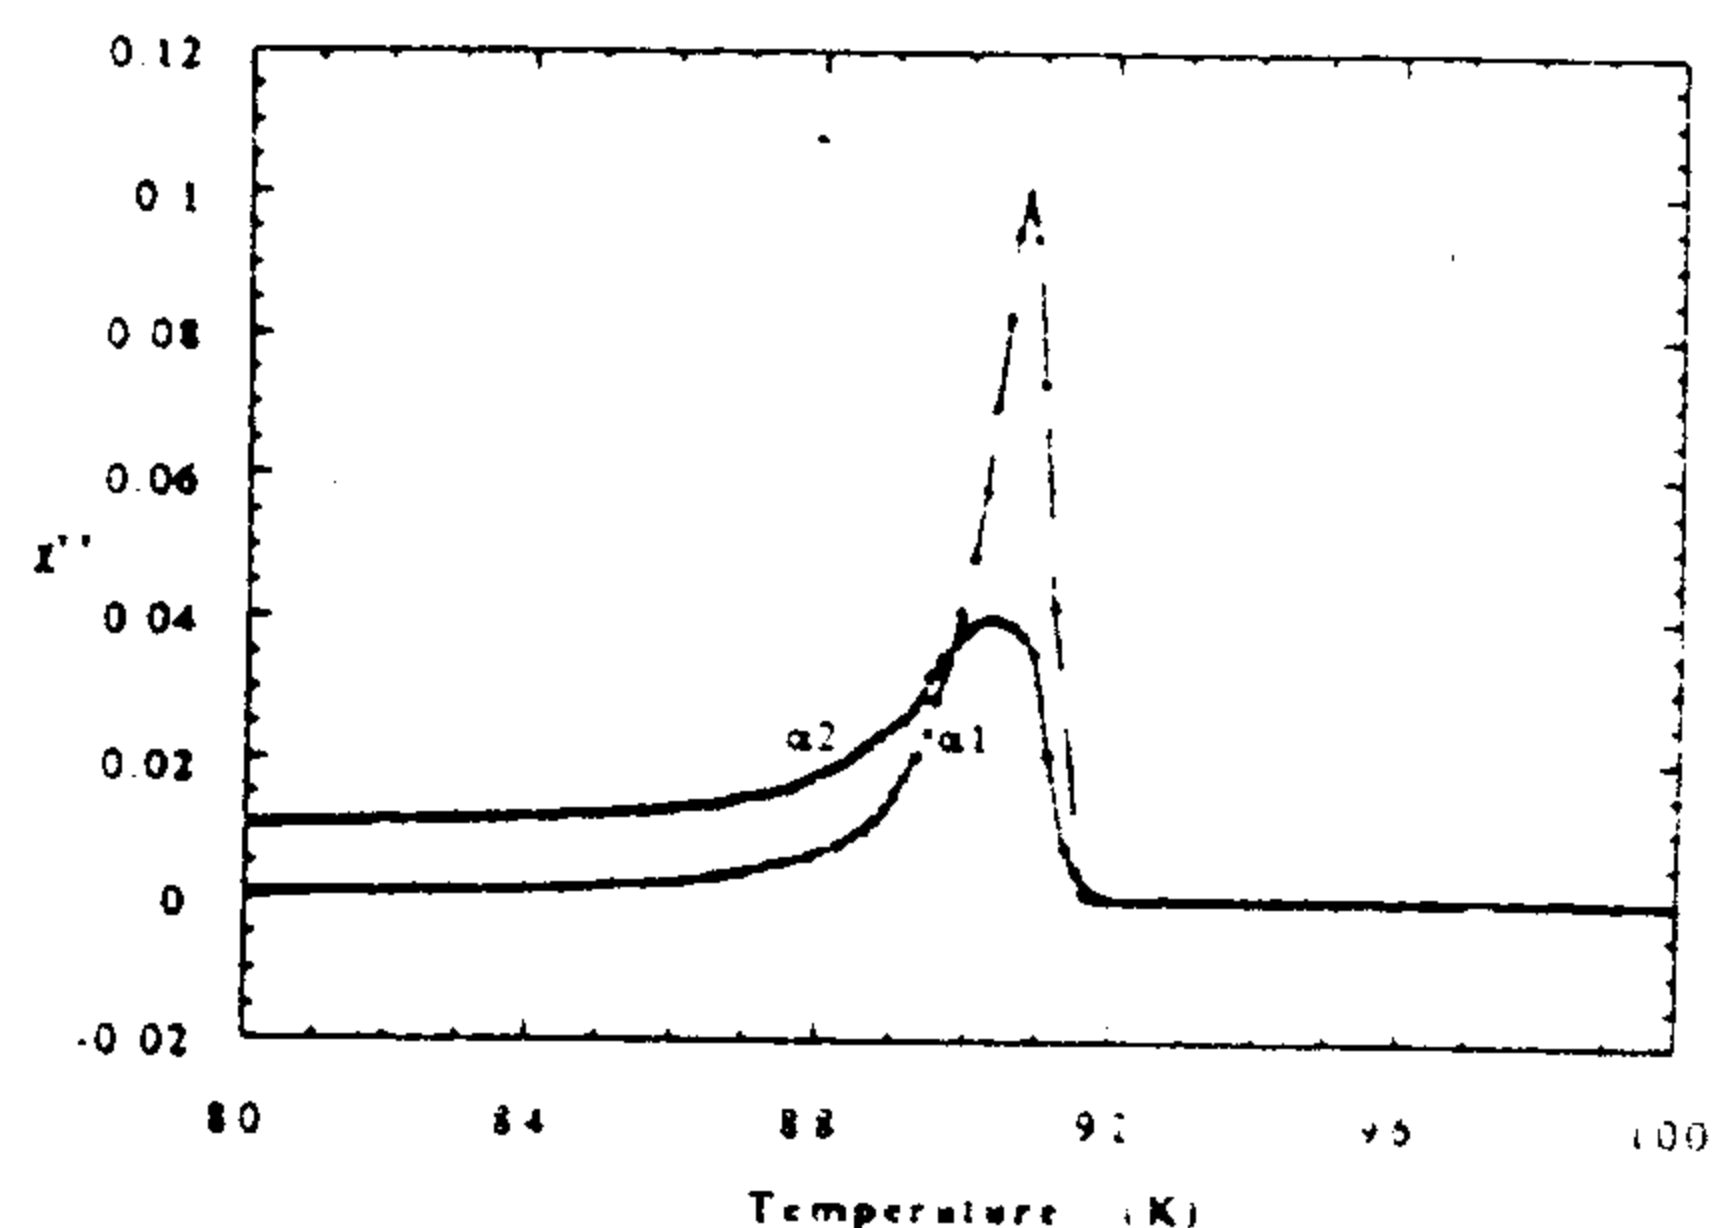


Fig. 3 - Imaginary part of the magnetic susceptibility (χ'') for the α sample. $\alpha 1$ YBCO pellet before H_2 loading; $\alpha 2$ YBCO sample after H_2 loading.

measurement before the loading and a value of χ'' at 77 K different from zero. From the above results, we can infer that in this case the hydrogen weakened the coupling without modifying the superconducting properties of the grain. In fact [12] the hydrogen loading

usually causes the precipitation of non-superconducting hydrides, which decouple the grains. Further on the precipitation should probably prevent the diffusion of the hydrogen into the grains, so that the variations of the superconducting properties [2] of the material are not allowed and the T_{0n} does not change.

A second pellet (β) was subjected to the charging for 2 hours with an higher pulse height (35 V, 15.2 A), but with a shorter width (1.3 μ s). In this way we nearly halved the area of the pulse. In fig. 4 and 5 the ac susceptibility measurements at 1 G and 107 Hz before ($\beta 1$) and after ($\beta 2$) the loading are compared.

In respect to the previous sample, we can observe an enhancement of the T_{0n} of about 5 K (95.2 K) without a significant enlargement of the FWHM.

In this case the loading did not substantially decrease the intergranular coupling, while it

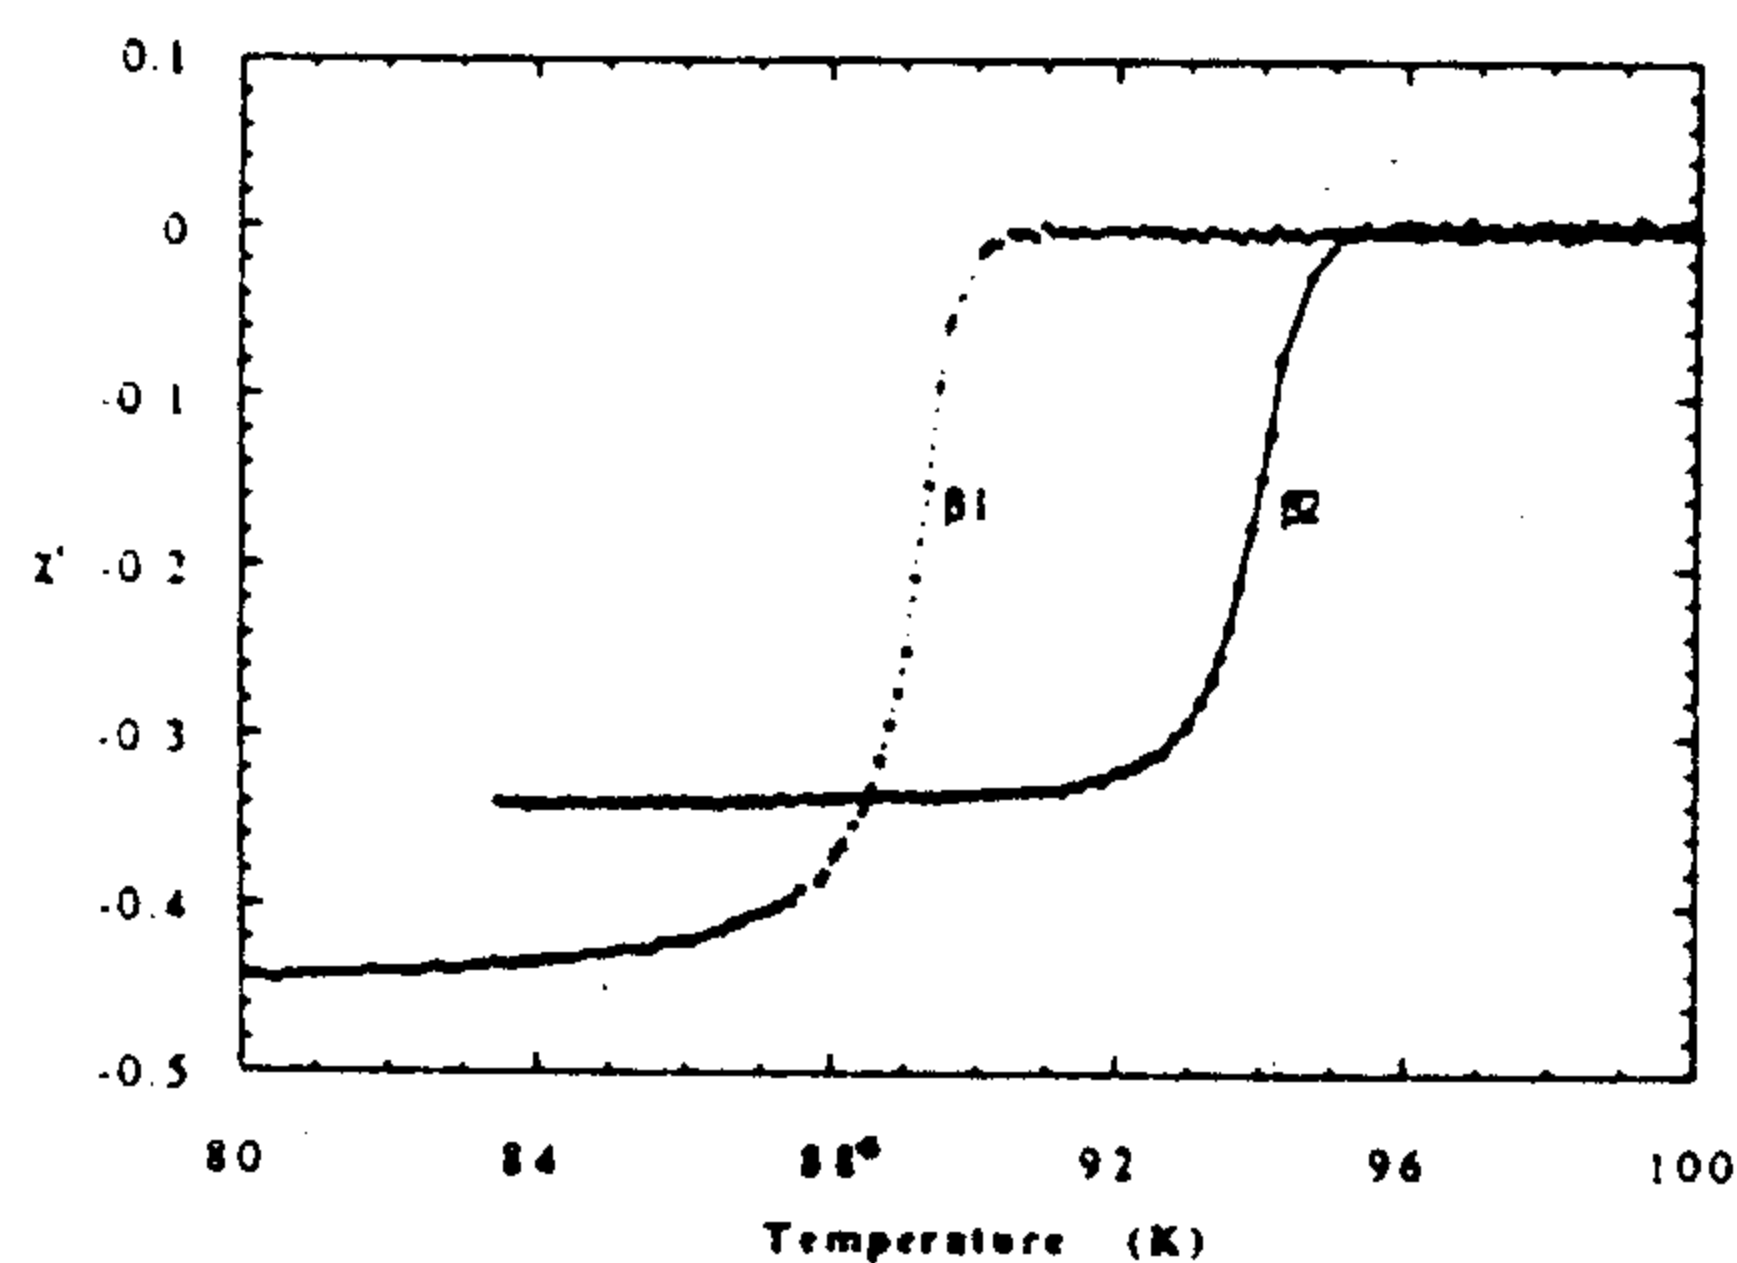


Fig. 4 - Real part of the magnetic susceptibility (χ') for the β sample. $\beta 1$ YBCO pellet before H_2 loading; $\beta 2$ YBCO sample after H_2 loading.

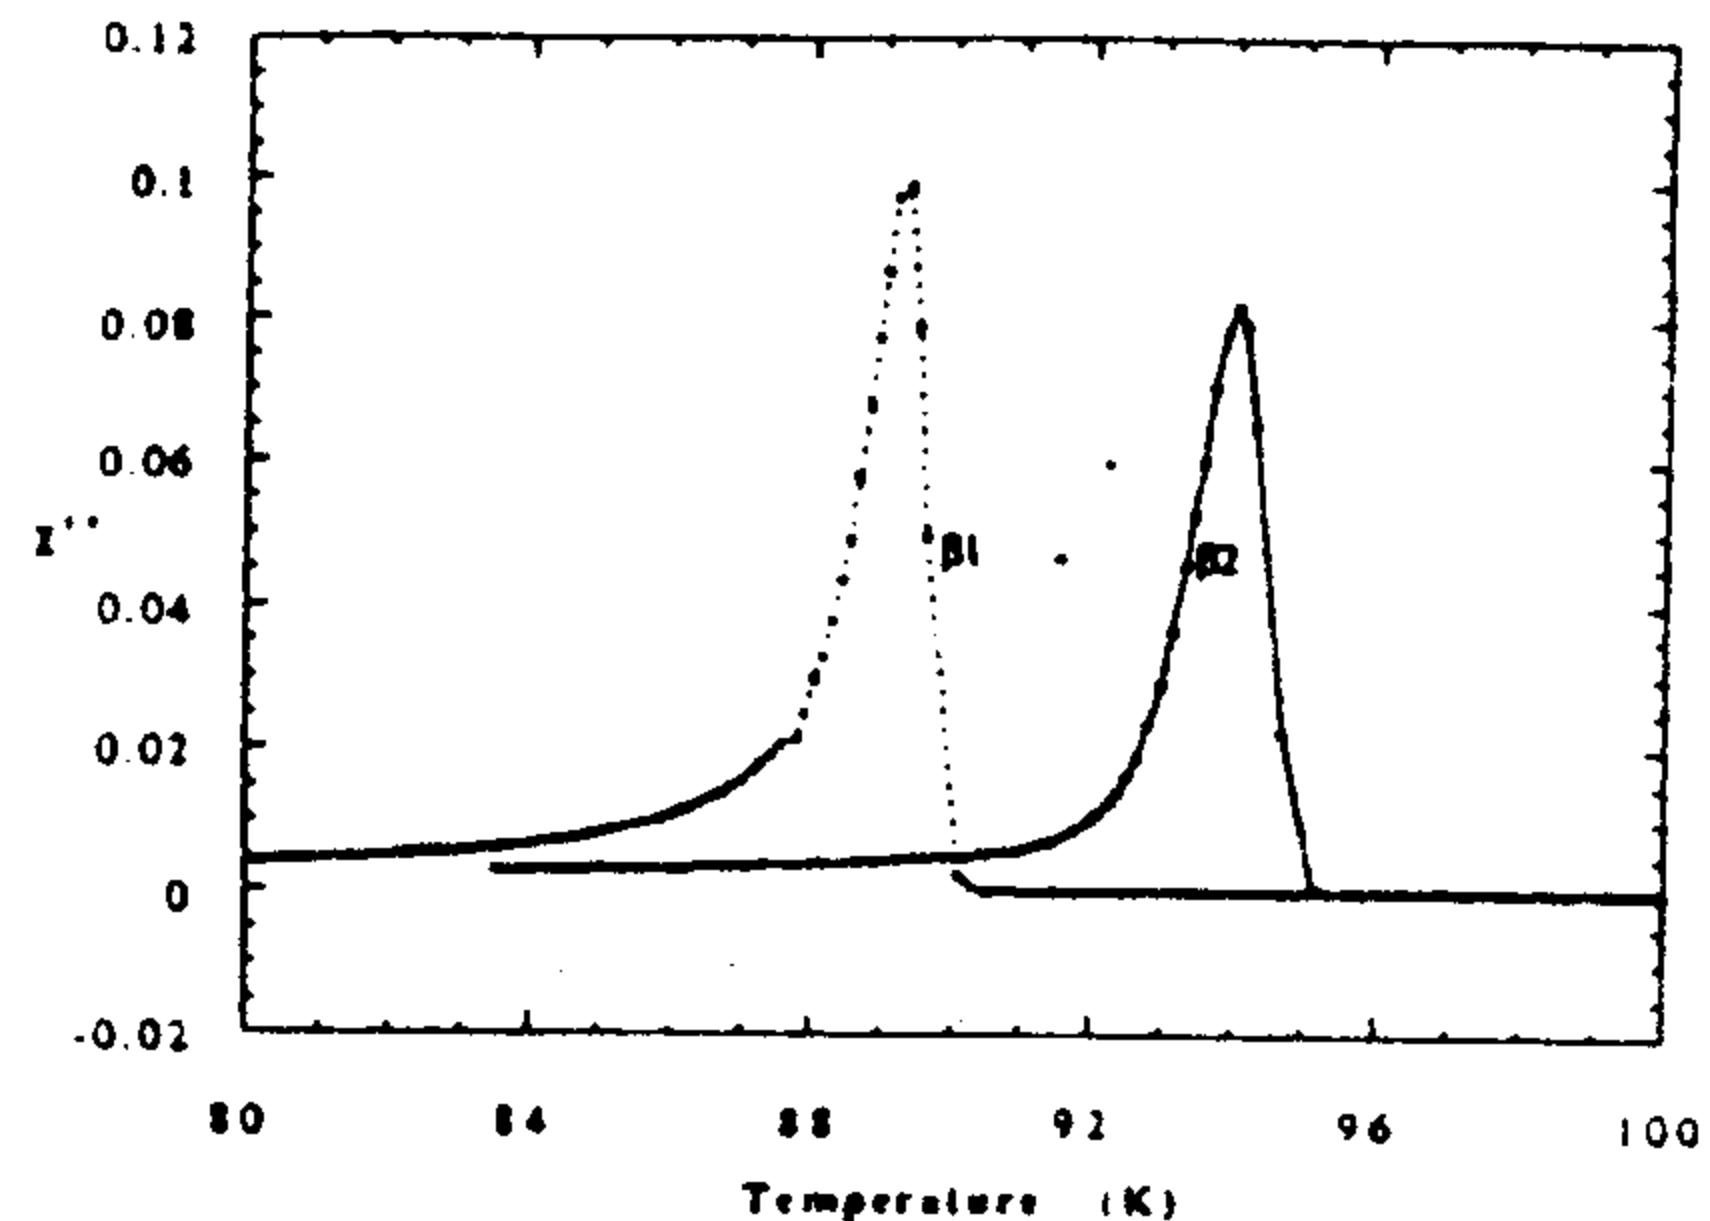


Fig. 5 - Imaginary part of the magnetic susceptibility (χ'') for the β sample. $\beta 1$ YBCO pellet before H_2 loading; $\beta 2$ YBCO sample after H_2 loading.

enhanced the transition temperatures. A possible explanation is that the higher pulse height determines an higher equivalent hydrogen pressure which allows the hydrogen to penetrate into the grains. Moreover in these conditions the precipitation of the hydrides at the grain boundaries seems not to give significant effects. During this charging the sample lost a little material, this fact could be related to the decreasing of the value of the modulus of χ' at 77 K.

After these positive results we decided to verify them with a further test, keeping constant the electrical parameters used for the electrolysis of the β sample. We loaded a new pellet (γ sample) for 120'. Subsequently the sample was cooled down to 77 K and the ac susceptibility was measured at 0.2 G and 1070 Hz during the warming up to 300 K. Afterwards the sample has been loaded for 30'

and the magnetic susceptibility has been measured warming again the sample. After the first charging, the temperature dependence of the imaginary parts, plotted in the curves γ_2 of fig. 6, shows a T_{On} enhancement from 91.7 K to 92.5 K without a meaningful variation of FWHM with respect to the curve γ_1 measured before the loading. On the contrary, as shown in the plot of χ'' (curve γ_3 of fig. 6) obtained after the second loading, the T_{On} decreased about 0.4 K in respect to the curve γ_1 , while the FWHM is not changed.

Because of the non-monotonic variation of the T_{On} , generated by two subsequent loadings, we decided to repeat this experiment in order to verify such a behaviour on the same sample, without changing any experimental condition. Between the first and the second couple of loadings 7 days elapsed with the sample kept at

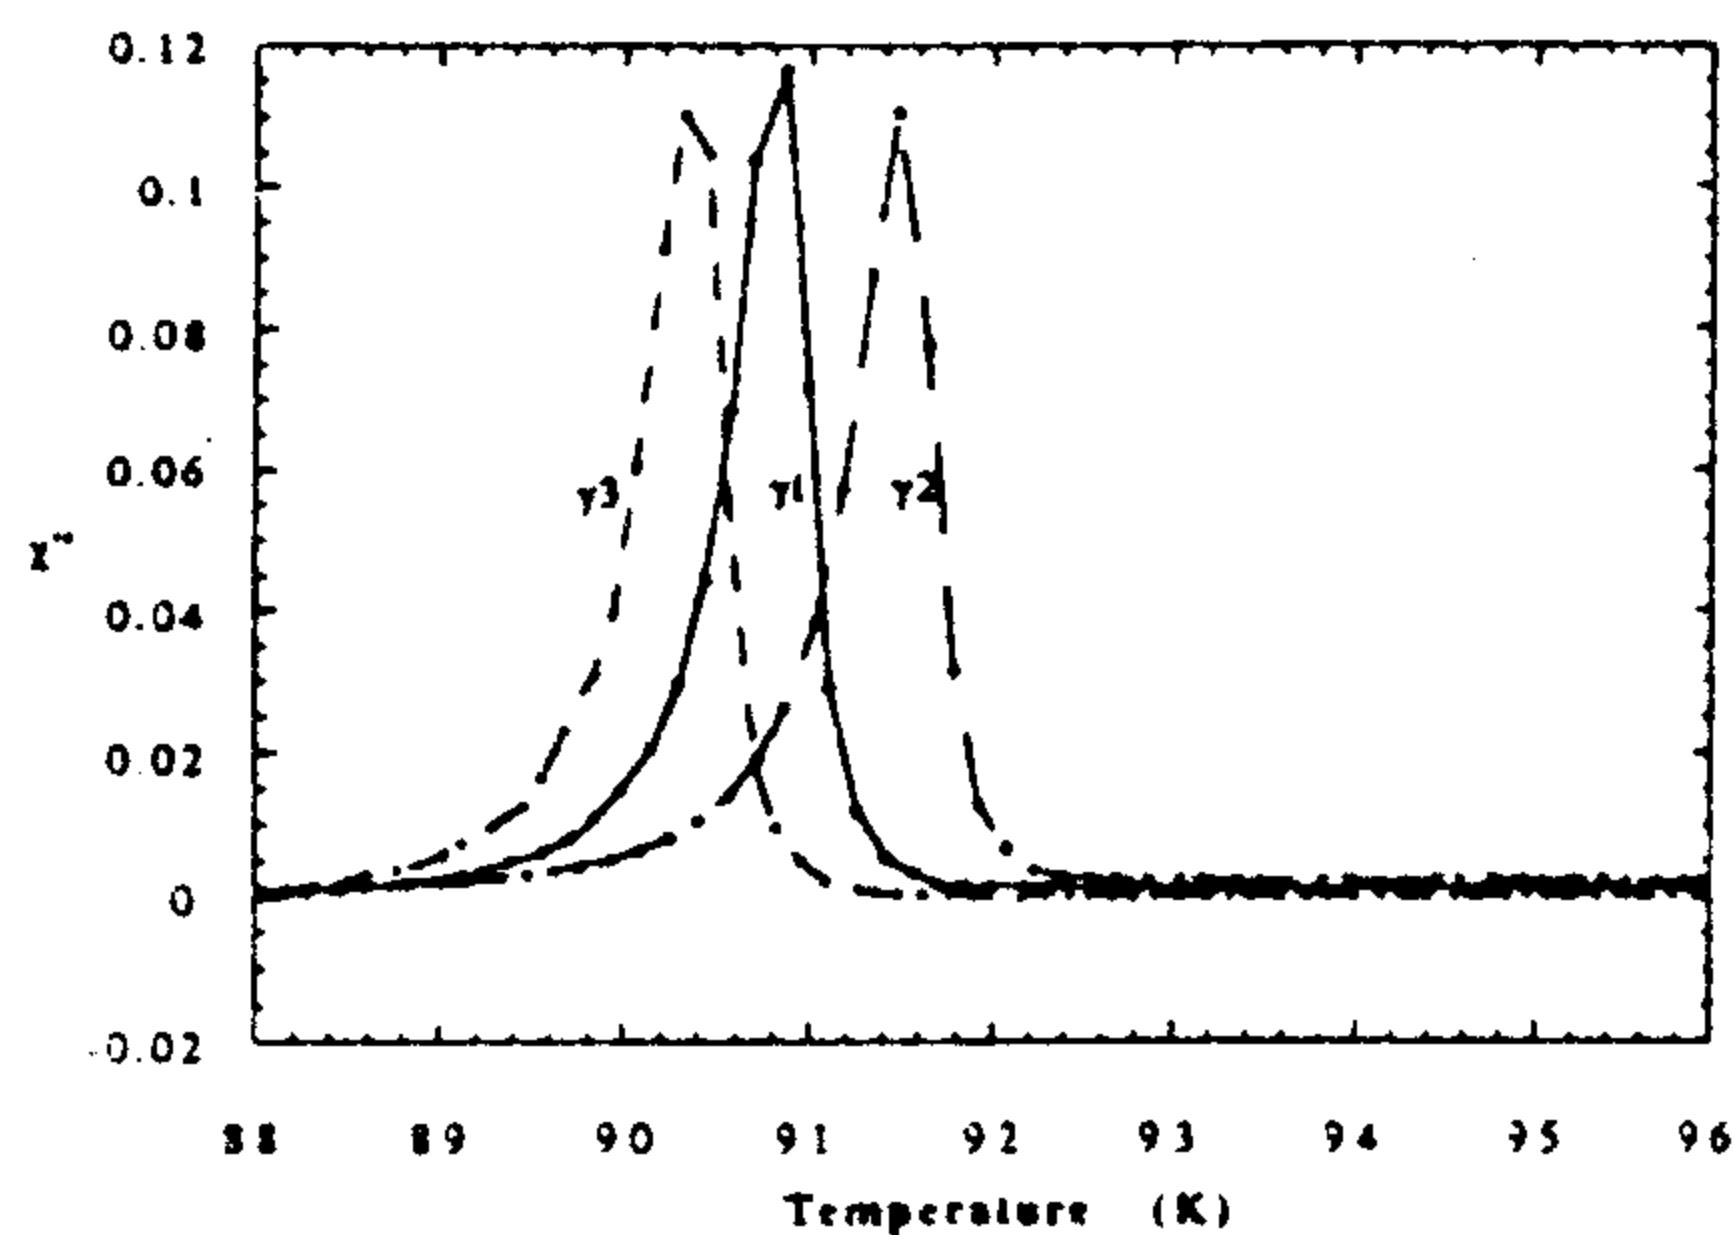


Fig. 6 - Imaginary part of the magnetic susceptibility (χ'') for the γ sample. γ_1 YBCO pellet before H_2 loading; γ_2 YBCO sample after the first H_2 loading (120'); γ_3 after the second H_2 loading (30').

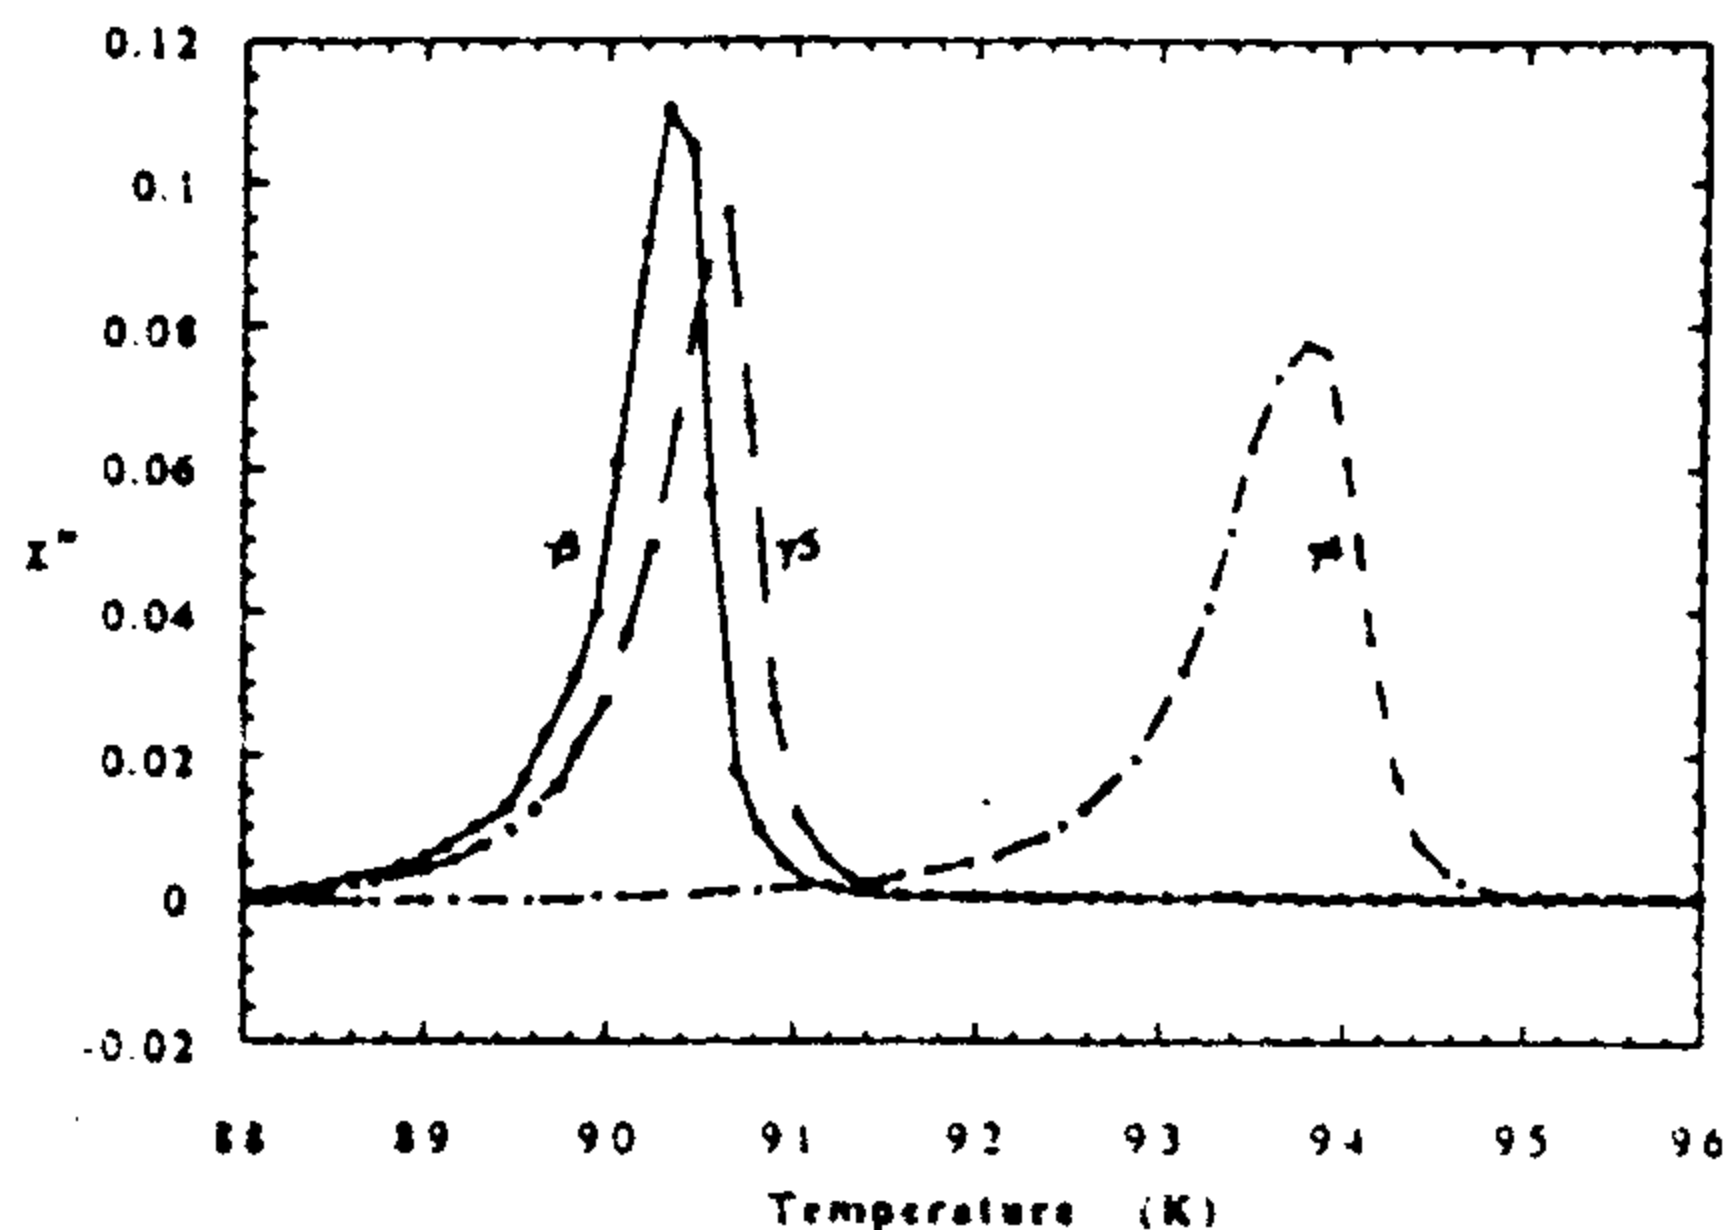


Fig. 7 - Imaginary part of the magnetic susceptibility (χ'') for the γ sample. γ_3 YBCO pellet after the second H_2 loading; γ_4 YBCO sample after the third H_2 loading (120'); γ_5 after the fourth H_2 loading (30').

room temperature in a closed environment. The susceptibility measurements are shown in fig. 7.

After the first loading (curve γ_4), T_{On} increased from 91.5 K to 95 K (3.5 K), while we observed an enlargement of FWHM. Later on the second loading (γ_5) T_{On} diminished of about 3.4 K, while FWHM showed values closed to the ones of γ_3 .

From the first two chargings (fig. 6) we can deduce that:

- a) since the FWHM does not increase, the hydrogen loading does not decrease the intergranular coupling between the grains, so that the quantity of spurious phases at the grain boundaries are not increased;
- b) the hydrogen penetrates into the grains and changes the critical temperature T_{On} .

Moreover in the first charging of the

second couple (fig. 7) there is a greater enhancement of the T_{0n} in respect to the first chargings and a broadening of FWHM due to a decreasing of the intergranular coupling. In this way it is possible to deduce that the pellet has a memory of the first couple of loadings, as the second one has been performed in the same experimental conditions, while different results are obtained.

As the last charging (and/or the thermal cycle) has restored the FWHM of the curve γ_5 to about the value of the curve γ_3 before the loading, the enlargement observed on γ_4 is reversible. For this reason, the effect can not be generated by hydrides precipitation, since in this case the enlargement of FWHM would have been permanent. The worsening could be due to an "overloading" of the pellet surface.

4. CONCLUSIONS.

The pulsed electrochemical method can be used to load quickly YBCO samples with hydrogen by means of an easy and safe experimental apparatus, if compared with our previous experience about the gas loading. In a reproducible way, with this procedure, we are able to increase the transition temperature of sintered pellets without weakening the superconducting coupling between grains. It clearly appears that these effects are dependent on the hydrogen equivalent pressure.

Anyway the effects of the hydrogen loading by pulsed electrolysis seems to be rather complex. In order to explain the non-

monotonic behaviour of the transition temperature with the number of loadings, three possibilities exist:

- 1 - the hydrogen may go out from the material during the thermal cycles, so that we are not sure that subsequent loadings increase the hydrogen content;
- 2 - a maximum of the transition temperature vs. the hydrogen content may exist;
- 3 - the loadings and/or the thermal cycles up to room temperature may arrange the hydrogen in different sites into the crystal structure, with different effects on the transition temperature.

In order to distinguish among the different possibilities, it should be necessary not only a measurement of the mean hydrogen content in the whole pellet, but its effective location.

We must consider two main aspects of the hydrogenation of the YBCO sintered pellet: the hydrogen quantity going into the grain and the hydrogen effects on the intergranular properties. It is very difficult for us to estimate the hydrogen quantity into the grain because of the following reasons.

The measurements of the H content are averaged on the whole bulk of the sample, in this way it is not considered the possible consequence due to different microscopic situations as the concentration gradient in the pellet: the H may be present in different sites in the crystal structure of YBCO giving different results. As a consequence in literature [1, 2, 4, 13] the authors give different relations between

the transition temperature and the hydrogen content (H/YBCO between 0.1 and 5, with a great difference in the superconducting properties of the H-YBCO composite). For example the weight difference (before and after the charging) measurement is not reliable because during the electrolysis some material fall down in the solution, and it is difficult to quantify the amount of water adsorbed in the sintered pellet. Besides, as some authors suggested, [13] the addition of hydrogen influences the superconducting properties similarly to oxygen removal: in our electrochemical case the hydrogen could reduce the oxygen in the YBCO. This tangled situation could explain the contradictions among results reported by different authors [1, 2, 4, 13-15] as far as the dependences of both T_c and of lattice parameters on hydrogen content is concerned. Up to now detailed measurements of the hydrogen content in our loaded pellets are not available. A systematic X-ray diffraction analysis and the evaluation of the mean hydrogen content by an electrochemical method and by the outgoing gases are in progress.

REFERENCES.

- [1] J.J. Reilly, M. Suenaga, J.R. Johnson, P. Thompson, and A.R. Moodenbaugh, *Phys. Rev. B* 36 (1987) 5694.
- [2] C.Y. Yang, X.Q. Yang, S. M. Heald, J.J. Reilly, T. Skotheim, A.R. Moodenbaugh, and M. Suenaga, *Phys. Rev. B* 36 (1987) 8798.
- [3] M. Nicolas, J. N. Daou, I. Vedel, P. Vajda, J. P. Burger, J. Lesueur, L. Dumoulin, *Solid State Comm.* Vol.66, No.11, (1988) 1157.
- [4] H. Fujii, H. Kawanaka, W. Ye, S. Orimo, H. Fukuba, *J.J. of Appl. Phys.* Vol. 27, No.4, April 1988, L525.
- [5] F. Celani, M. Boutet, D. Di Gioacchino, A. Spallone, P. Tripodi, S. Pace, M. Polichetti, *Phys. Lett. A*, 183 (1993), 238.
- [6] H. Wenzl, J.-M. Welter: *In Current Topics Mater. Sci.* 1, 603 (North-Holland, Amsterdam 1978)
- [7] M. Enyo, *J. Electroanal. Chem.*, 134 (1982) 75-86
- [8] M. Enyo and P.C. Biswas, *J. Electroanal. Chem.*, 335 (1992) 309-319
- [9] F. Celani, A. Spallone, P. Tripodi, A. Nuvoli, A. Petrocchi, D. Di Gioacchino, M. Boutet, P. Marini, V. Di Stefano, "High power μ s pulsed electrolysis for large deuterium loading on Pd plates", Invited Paper at Fourth International Conference on Cold Fusion, Dec 6-9, 1993 Lahaina, Maui (U.S.A.), publishing on Electrical Power Research Institute (U.S.A.), 1994

- [10] "Magnetic Susceptibility of Superconductors and Other Spin Systems", Edited by Hein, Plenum Press, New York and London (1991)
- [11] F. Celani, A. Saggese, S. Pace, L. Liberatori, N. Sparvieri, *Mat. Chem. and Phys.* 25 (1990) 43.
- [12] C.Y. Yang, S. M. Heald, M. W. Ruckman, J.J. Reilly, and M. Suenaga, *Physica B* (1989) 484.
- [13] Goren et al., *Phys. Rev. B*, 42, 13 (1990) 7949
- [14] M.V. Abrashev, Bozukov, M.N. Iliev, *Physica C* 178 (1991) 317-323
- [15] Wang, Pang, Luo, Yang, Li Ji, Sun, *Phys.Lett.A* Vol 130, n. 6,7 405 (1988)
- [16] T. Takabe, W. Ye, S. Orimo, T. Tamegai, and H. Fuji, *Physica C* 162-164 (1989) 65.
- [17] F. Celani, A. Spallone, L. Liberatori, B. Stella, F. Ferrarotto, M. Corradi, P. Marini, S. Fortunati, M. Tului, "Anomalous Nuclear Effects in Deuterium/Solid System" AIP Conference Proceeding 228, Provo UT, (1991) 62, S. E. Jones, F. Scaramuzzi, D. H. Worledge eds.
- [18] G Alefeld, J. Volkl (eds.): "Hydrogen in metals II, Application-Oriented Properties". *Topics in Applied Physics*, vol. 29 (Springer, Berlin: Heidelberg, New York 1978).